

ALKALINE STRIPPING FOR ULTRA CLEAN BITUMEN FROM TAR SAND

R.T. Akande^{1#}, A.A. Adeleke¹, P.O. Atanda¹

¹Obafemi Awolowo University, Department of Materials Science and Engineering, Ile-Ife, Nigeria

(Received: August 27, 2018; Accepted: June 7, 2019)

Abstract

This study reports the recovery of bitumen concentrate from Ondo tar sand by alkaline leaching stripping of the associated sand. Bitumen was extracted from the tar sand as received in un-stirred and stirred state in the oven and on the magnetic stirrer hotplate, respectively, at varying 3² factorial design combinations of temperature and sodium hydroxide molar concentrations at 40 g/dm³ pulp density. The tar sand was further subjected to bitumen dissolution test and recovery of bitumen at varying pulp density. The results obtained showed that bitumen was optimally stripped from the tar sand with initial bitumen content of about 34% in the stirred condition to produce a concentrate with grade and recovery percents of 98.82 and 99.41% of bitumen, respectively. The optimal leaching stripping was obtained at 2 M sodium hydroxide concentration, at 90 °C temperature and 25 minutes contact time. The ultra-clean bitumen obtained can serve as raw material input for petroleum products recovery and as a coking additive in blend formulation of coals for metallurgical coke making.

Key words: Tar sand; Bitumen; Leaching; Grade; Recovery; Cokemaking

1. Introduction

Tar sands also known as oil sands, are a combination of clay, sand, water, saturated with a dense and extremely viscous form of petroleum technically referred to as bitumen. They are impregnated sands that yield mixtures of liquid hydrocarbons, which require further processing other than mechanical blending before becoming finished petroleum products. Tar sand is found in various parts of the world including Canada, Madagascar, Venezuela, Russia, United States and Nigeria [1]. It is exceedingly rich in oil and other valuable minerals and metals in varying proportions. The tar sand deposits are composed primarily of quartz sand silt and clay, water and bitumen along with minor amount of metal minerals such as rutile, pyrite and zircon and gemstone like tourmaline [2].

Typically, oil sands contain about 75 percent inorganic matter, 10 to 18% bitumen, 10% silt and clay, and 5% water. The bitumen has high density, high viscosity, and high metal concentration. Oil sands are also low in hydrogen due to high carbon

carbon-to-hydrogen molecule count. This thick, black, tar-like substance must be upgraded with an injection of hydrogen or by the removal of some of the carbon before it can be processed [3 - 5].

The bitumen content is what makes the oil sands a valuable energy resource. The bitumen content can vary within a deposit from 1 to 18%. Once it is extracted from the sands, bitumen can be upgraded into crude oil and then refined into common petroleum products such as gasoline, kerosene or gas oil [4]. Nigeria has the fourth world largest deposit of natural bituminous tar sand estimated to be 31 billion metric tons in Ondo state alone with more reserves in Edo and Ogun States [6]. The bituminous materials, apart from the use in the production of crude oil, is useful in the petrochemical industry. The sulphur content of Nigeria tar sand constitutes a potential source of elemental sulphur for sulphuric and superphosphate fertilizer production plants. Other industrial applications include production of anticorrosive coatings, protection for electric cable, bonder adhesives and brake lining [7]. Bitumen extract from tar sand is also

#Corresponding author: akanderukayat2@gmail.com

doi: 10.5937/JMMA1901017A

used as an additive in the production of metallurgical grade coke [8, 9].

The presence of water layer around the sand grains enables the bitumen to be recovered more easily since the bonding forces between the bitumen and water are much weaker than those between the water and the sand grains [10, 11]. Ondo tar sand was leached using sodium hydroxide and sodium carbonate for recovery of bitumen and also solubility test carried out on the tar sand using toluene [12]. Sodium hydroxide gave higher percentage of recovery than sodium carbonate for the same leach contact time. The bitumen recovery in the work was 98.05% with a bitumen grade of 97.70%.

The present research is designed to obtain bitumen of grade and recovery exceeding 97.70 and 98.05%, respectively; Ondo tar sand by factorial design based combinations of the leaching process variables in un-stirred and stirred conditions.

2. Materials and methods

2.1. Materials

2.1.1. Sample collection

The basic raw materials used in this work were lumps of bituminous tar sand obtained from Ondo State, Nigeria. About 50 kg lumps of the semi-solid black tar sand were collected from Agbabo-Loda village in Irele Local Government of the state. Irele Local Government is on the eastern boundary of Okitipupa Local Government which lies on longitude 40°3" East of Greenwich Meridian and Latitude 50°45" and 80°15" North of the Equator. The choice of this location was based on the availability of plain bitumen in the zone coupled with its accessibility. The sample was collected from 2 open pits at a depth of about 3 feet. After the field sampling, the lumps of tar sand obtained were kept in large plastic bags.

2.1.2. Sample preparation

The tar sand black lumps were crushed and properly ground with a steel rod. The ground tar sand was then homogenized in a mortar by

pounding with a pestle. The resulting tar sand mass gave a finer particle and bitumen mixture.

2.1.3. Methods

2.1.3.1. Solubility test

One gram of the homogenized tar sand was placed in 0.25 dm³ beaker and 25 cm³ of 99.5% toluene was added to make a slurry at about 40 g/dm³ pulp density. The mixture was stirred with a glass rod for 2 minutes and left to react for 1 minute. The test was carried out in duplicates. The test was repeated for 2, 3, 4, 5, 6 and 7 minutes of reaction. A blank test was as well carried out using water instead of toluene for these durations.

2.1.3.2. Atmospheric oven leaching

The tar sand was leached in laboratory oven model number LKM DHG-9101-1SA using 3² factorial design, with temperature and concentration as process variables. The tar sand was leached at three different temperatures - T₁, T₂ and T₃ where T₁ = 50 °C, T₂ = 70 °C and T₃ = 90 °C and three different concentrations of sodium hydroxide C₁, C₂, C₃ where C₁ = 0.5 M, C₂ = 1 M and C₃ = 2 M. The nine combinations of the leaching T₁C₁, T₁C₂, T₁C₃, T₂C₁, T₂C₂, T₂C₃, T₃C₁, T₃C₂ and T₃C₃ are shown in Table 1. One gram of tar sand as received was placed in 25 ml 0.5 M sodium hydroxide in a 0.25 dm³ erlenmeyer flask reactor. The slurry was then homogenized by stirring for 5 minutes and covered with Al foil.

One gram of tar sand as received was placed in 25 cm³ 0.5 M sodium hydroxide in a 0.25 dm³ erlenmeyer flask reactor. The slurry was then homogenized by stirring for 5 minutes, covered with Al foil and transferred into the oven for leaching. The oven was set at 50 °C to give the test combination T₁C₁ and left for 30 minutes after attaining the set temperature. The bitumen concentrate was skimmed off, dried and weighed. The bitumen concentrate was also tested for grade and recovery as described below. The procedure was repeated for test combinations T₁C₂, T₁C₃, T₂C₁, T₂C₂, T₂C₃,

T₃C₁, T₃C₂ and T₃C₃. A blank test was as well carried out using 25 cm³ of distilled water at about 40 g/dm³ pulp density in a 0.25 dm³ erlenmeyer flask reactor. The slurry was stirred for 5 minutes to homogenize it and then transferred into the oven for leaching at 90 °C for 30 minutes.

Table 1. Factorial combinations of leaching variables

Temperature	Concentration	Combination
T ₁	C ₁	T ₁ C ₁
T ₁	C ₂	T ₁ C ₂
T ₁	C ₃	T ₁ C ₃
T ₂	C ₁	T ₂ C ₁
T ₂	C ₂	T ₂ C ₂
T ₂	C ₃	T ₂ C ₃
T ₃	C ₁	T ₃ C ₁
T ₃	C ₂	T ₃ C ₂
T ₃	C ₃	T ₃ C ₃

2.1.3.3. Determination of optimal leaching time

The sample slurry at about 40 g/dm³ in erlenmeyer flask reactor covered with Al foil was leached on Stuart magnetic stirrer model no R000101019 for 5 minutes contact time in 1 M sodium hydroxide solution at 90 rev/min. After 5 minutes, the erlenmeyer flask reactor was removed from the magnetic stirrer hotplate and the bitumen was skimmed off. The test was repeated at 1.5, 2, 2.5, 3, 3.5 and 4 M concentrations and varied contact times of 10, 15, 20, 25 and 30 minutes. The procedure was repeated for 10, 15, 20, 25 and 30 minutes contact time.

A blank test was also carried out using at the same 40 g/dm³ pulp density in a 0.25 dm³ erlenmeyer flask reactor. The slurry was stirred for 5 minutes to homogenize it and the erlenmeyer was covered with an aluminium foil and then placed on the magnetic stirrer hotplate which agitates the slurry.

2.1.3.4. Leaching on magnetic stirrer hot plate

The tar sand was leached on a magnetic stirrer hotplate using 3² factorial design, that is, at three

levels of temperature and concentration process variables as in section 3.2.3. The 0.25 dm³ beaker reactor with tar sand slurry having 25 cm³ 0.5 M sodium hydroxide at about 40 g/dm³ pulp density was initially homogenized for 5 minutes. The beaker was placed on Stuart magnetic stirrer hotplate model number R000101019, the magnetic stirrer was set to 50 °C and 90 rev/min to give the T₁C₁ test combination. The magnetic stirrer was switched on and the tar sand pulp was allowed to react with the sodium hydroxide leachate for 30 minutes. At the end of the 30 minutes, the bitumen concentrate was skimmed off and the leachate was filtered to remove the remaining bitumen. The procedure was repeated for combinations T₁C₂, T₁C₃, T₂C₁, T₂C₂, T₂C₃, T₃C₁, T₃C₂ and T₃C₃.

2.1.3.5. Determination of bitumen recovery and grade

The mass of bitumen in the concentrate was determined by dissolving the bitumen obtained from each of the T₁C₁ combination with 25 cm³ of toluene for 10 minutes contact time at the same pulp density of 40 g/dm³. The leaching of the concentrate with toluene was carried out for 10 minutes until the bitumen was fully dissolved from the associated sand. The remaining sand was dried, weighed and the value was subtracted from the initial mass of the tar sand to determine the mass of the bitumen in the concentrate. The leachate was filtered to remove excess sand. The test was repeated for the T₁C₂, T₁C₃, T₂C₁, T₂C₂, T₂C₃, T₃C₁, T₃C₂ and T₃C₃ combinations.

The recovery and grade was calculated as follows:

$$\% \text{ Recovery} = \frac{\text{mass of bitumen in the concentrate}}{\text{mass of bitumen in tar sand sample}} 100 \quad (1)$$

$$\% \text{ Grade} = \frac{\text{mass of bitumen in the sample/concentrate}}{\text{mass of sample/concentrate}} 100 \quad (2)$$

2.1.3.6 Leaching stripping of sand on electric hotplate

A tar sand slurry of about 40 g/dm³ pulp density prepared by mixing 25 cm³ 1.5 M of sodium

hydroxide and 1 g of tar sand in a 0.50 dm³ beaker. The beaker with the tar sand slurry was then placed on the HP-11 electric hot plate. The slurry was stirred continuously with a glass rod to agitate it for the recovery of bitumen from the tar sand. This was done for 30 minutes and after that the bitumen was decanted off and the residue was washed with water to remove bitumen. The residue was further washed with toluene to dissolve traces of bitumen in the tailings. The residue was then dried at 70 °C in the oven. The procedure was then repeated for 2, 3, 4, 5, 6, 7, 8, 9 and 10 g translating to about 80, 120, 160, 200, 240, 280, 320 and 400 g/dm³ pulp density, respectively. The same procedure was further repeated using 30 g of tar sand and the slurry was prepared by mixing 0.30 dm³ 1.5 M of sodium hydroxide and 30 g of tar sand in a 0.50 dm³ beaker. The procedure was repeated severally until 7 kg of tar-free sand was recovered. A blank test was carried out using 25 ml of distilled water and 1 g tar sand in a 0.50 dm³ beaker reactor. The beaker with the tar sand slurry was then placed on the HP-11 electric hot plate. The slurry was stirred continuously with a glass rod to agitate it for the recovery of bitumen from the tar sand.

3. Results and discussion

After leaching the tar sand as-received with toluene for 3 minutes, the bitumen recovery was 34%. Table 2 shows that the peak time for leaching bitumen in toluene is 3 minutes. It was also observed that water could not strip bitumen from the tar sand despite its longer contact time with the sample as the tar sand remains the same mass. Figure 1 shows the mass of the sand residue determined as a function of time. It was observed that the bitumen in the tar sand gets completely dissolved in toluene after 3 minutes as there was no further increase in residual sand mass after 3 minutes. The percent bitumen grade and recovery obtained were 98.82 and 99.41% which is higher than 97.70 and 98.05% obtained by Adeleke et al. [12]. Hence, there is an improvement in the recovery of the bitumen and its grade to ultra clean state. The initial content of about 34% bitumen or extra heavy

crude oil in the Ondo oil sand is much higher than the typical 10% in oil sands in other countries [2]. The improvement obtained may be due to the increased pulp stirring applied during the bitumen stripping stage, higher concentration of the leachate or a combination of these factors [13].

Table 2. Peak time for leaching of bitumen in toluene

Contact time (minutes)	Sand Residue (g)
1	0.74
2	0.72
3	0.66
4	0.66
5	0.66
6	0.66
7	0.66

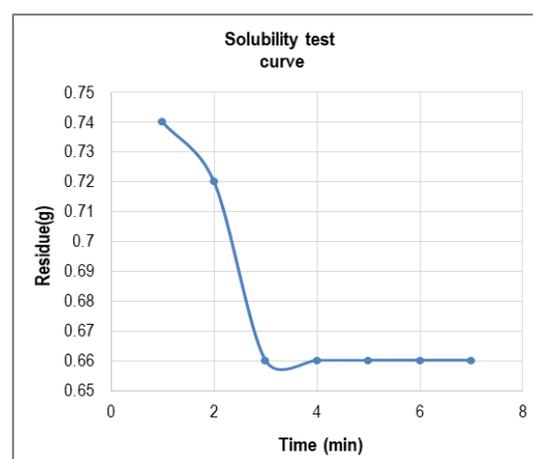


Figure 1. Residual sand recovered with increasing contact time when tar sand was dissolved in toluene

3.1. Determination of the optimal concentration and temperature

Table 3 lists the grades and recoveries obtained at different combination of temperature and concentration of sodium hydroxide for leaching of bitumen on magnetic stirrer hotplate. It was observed that the combination T₃C₃ (T₃ = 90 °C and C₃ = 2 M) gave the best grade and recovery percents of 98.82 and 99.41%, respectively. The results strongly indicate that temperature and concentration of the leachate determines the

effectiveness of the leaching which in turn determines the grade and the recovery of the bitumen obtained. The product obtained is ultra clean. The blank test showed that water cannot successfully strip bitumen from tar sand using a magnetic stirrer as the tar sand remained unchanged. A bitumen concentrate with grade and recovery percents of 98.82 and 99.41%, respectively were obtained which are higher than 98.05% recovery and 97.70% grade obtained in earlier work [12]. Hence, bitumen from Ondo tar sand has been recovered with higher grade and recovery.

Table 3. Grades and recoveries of bitumen recovered for the 3^2 factorial design experiment on the magnetic stirrer hotplate

Combination	Grade (%)	Recovery (%)
T ₁ C ₁	55.00	97.06
T ₁ C ₂	65.40	97.65
T ₁ C ₃	79.10	98.24
T ₂ C ₁	62.96	98.82
T ₂ C ₂	68.00	99.41
T ₂ C ₃	97.14	99.41
T ₃ C ₁	84.60	98.82
T ₃ C ₂	91.89	99.41
T ₃ C ₃	98.82	99.41

The grade and recovery rate at different combination of temperature and concentration are also shown in Figure 2. The graph indicates that the leaching rate is greatly influenced by concentration and temperature as good grades and recoveries were observed as the temperature and the concentration increase. The maximum positive leaching effect was observed at the highest temperature of 90 °C and highest molar concentration of 2 M. The (T₃C₃) combination thus had the best recovery and grade values. It has been established in literature that leaching rate generally increases with increasing temperature and concentration of the leachate [13]. An equation was developed which showed that the leaching rate of gibbsite increases almost squarely with concentration and exponentially with temperature [13].

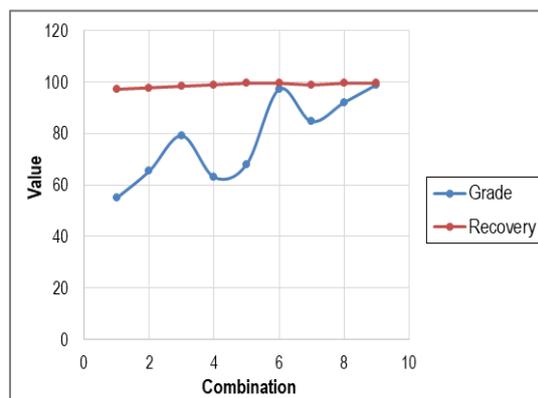


Figure 2. Grades and recoveries of bitumen at factorial combinations of temperature and concentration

3.2. Determination of the effect of slurry stirring

Figure 3 shows that there was only minor bitumen separation after 30 minutes of leaching tar sand in the oven, the highest recovery being about 41% of the initial mass of the sample treated. The use of increasing sodium hydroxide leachate concentrations of C₁ = 0.5 M, C₂ = 1.0 M, and C₃ = 2.0 M increasing temperatures of T₁ = 50 °C, T₂ = 70 °C and T₃ = 90 °C produced only minor yield in bitumen. In contrast, the yield of bitumen on the magnetic stirrer hotplate within the same contact time was significantly higher at 99.41% of the initial mass of the sample (Table 3). Hence, the result shows that the stirring action was more important than both temperature and concentration variables whose increases produced low bitumen yield after 30 minutes of the oven leaching. Furthermore, the oven leaching result shows that water is not a potent leachate as it had no effect on the stripping of bitumen from the tar sand for all the leaching contact times. Stirring agitation of slurry has been reported to produce increase leaching rate [13]. The results obtained strongly suggests that the semi-pilot and pilot scale upgrading of the present research should be carried out with a magnetic stirrer or autoclave system under intense stirring because of the increased pulp density at say 7 and 250 kg mass, respectively.

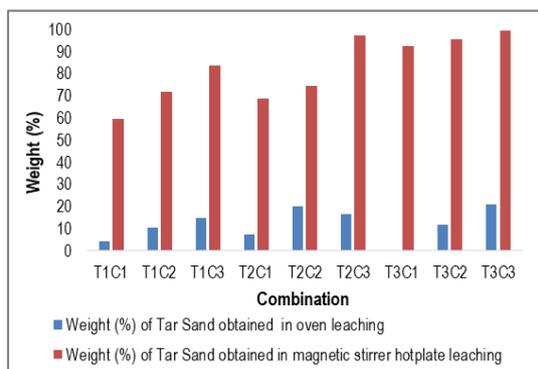


Figure 3. Leaching recovery of bitumen from tar sand in oven and magnetic stirrer after 30 minutes

3.3. Determination of optimal leaching time

Figure 4 shows the mass of the residue after the bitumen was leached away as a function of concentration and contact time process variables. It was also observed from the blank test, that water is not a potent leachate for stripping bitumen from the tar sand as the mass of the tar sand remained unchanged after 30 minutes contact with water leachate.

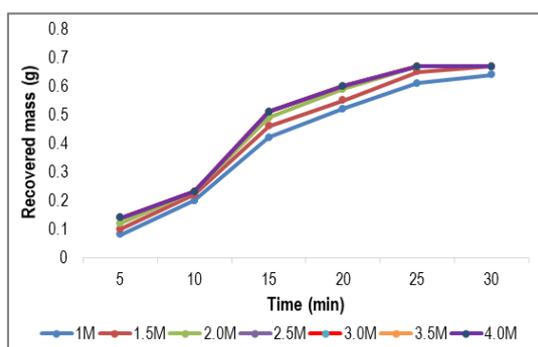


Figure 4. Recovered mass of tar free sand at different concentrations and contact time in magnetic stirrer hot plate leaching

It was observed from Figure 5 that the bitumen leaching from the tar sand was also time dependent as the tar sand must have sufficient contact time with the leachate for the leaching reaction to take place. Figure 5 also indicates that the time required for the leaching to occur was also dependent on the concentration of the leachate. At higher

concentration, lesser time was required unlike at lower concentration. The peak bitumen recovery of 99.41% was obtained at 25 minutes contact time for 2.0 M leachate concentration. The increase of the contact time beyond 25 minutes did not yield higher bitumen recovery. It was also observed that a decrease in the molar concentration required an increase in the contact time for the bitumen recovery.

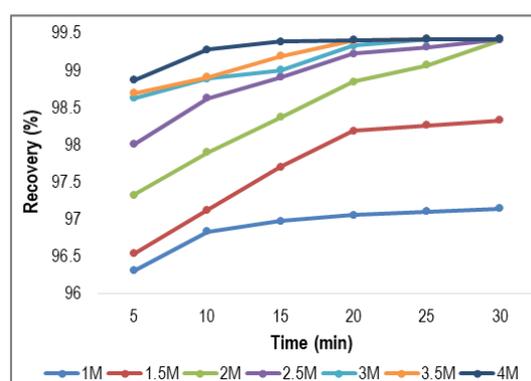


Figure 5. Recovery (%) of bitumen at different concentrations and contact time on magnetic stirrer hot plate leaching

The composite graph, Figure 5, shows that the mass of bitumen leached increases with increasing contact time and increasing leachate concentrations. It could be seen from the curves that bitumen recovery was low at 5 minutes and increased with contact until the maximum was attained at 25 minutes at each concentration. It was observed that the percentage recovery and grade increases with increasing contact time and increasing leachate concentration. Figure 4 shows that the mass recovered at 10 minutes contact time was almost the same for 1.5 to 4 M concentrations. It was further observed that the mass recovered also became almost equal after 30 minutes contact time for concentrations 1.5 to 4 M and is only marginally higher, that is, 0.019 g, than that at 1 M concentration. The results obtained suggest that leaching at 1 and 2 M lower concentrations may be sufficient in economic term. Figure 5 shows that the bitumen recovery percentage generally increases with increasing contact time and concentration.

However, it was observed that the recovery percentage becomes almost equal for molar concentrations 2 to 4 M at 30 minutes contact time. This further strongly suggests that a lower concentration of 2 M may be sufficient to obtain the highest bitumen recovery after the 30 minutes contact time. The contact time of 30 minutes is further shown to be an optimal leaching duration. Leaching tests carried out at concentration between 0.1 and 3 M, with a small variation between each concentration, showed that there is an increase in rate of leaching with increase in concentration, however, further increasing of the concentration leads to decrease in rate of leaching. Figure 6 shows that grade % generally increase with contact and molar concentration and became equal for the 1.5 to 4 M concentrations at 10 minutes and then for 2 to 4 M at 30 minutes contact time. The results again strongly suggest that leaching at 2 M concentration at a contact time of 30 minutes may be sufficient and hence most economical.

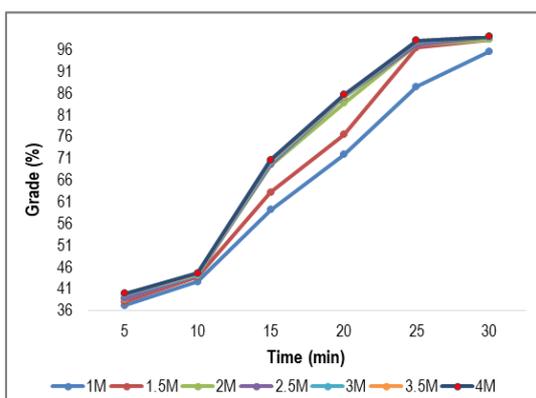


Figure 6. Grade (%) of recovered bitumen at varying concentration of sodium hydroxide and contact time on magnetic stirrer hot plate leaching

3.4. Leaching stripping of sand on electric hotplate

The weight percent of recovered tar-free sand reduces with increase in the mass of the tar sand, as shown in Figure 7, which indicates that the percentage recovery decreases as the pulp density increases. Hence, pulp density is one of the factors

that affect leaching and hence the bench scale leaching was carried out at about 40 g/dm³. It was observed that the least bitumen recovery of 55% on the magnetic stirrer hotplate was higher than the highest recovery of 45% on the ordinary hotplate. This confirms that slurry stirring is an important process variable in leaching hydrometallurgy [13].

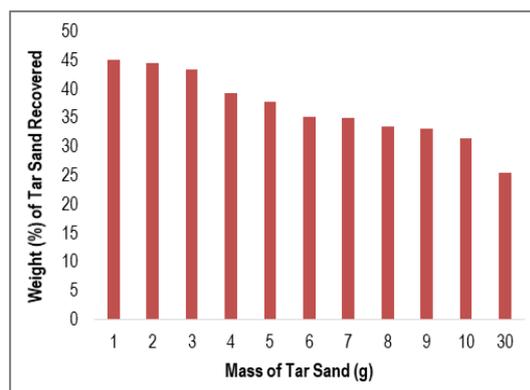


Figure 7. Weight (%) of tar sand recovered on stripping on electric hot plate

3.5. Mechanism of leaching bitumen

Each grain of tar sand is surrounded by a film of water that is in turn covered by the heavy bitumen oil. The presence of water layer around the grains enables the bitumen to be recovered more easily since the bonding forces between the bitumen and water are much weaker than those between the water and the sand grains [10]. The alkaline leaching caused neutralization of organic acids with the formation of natural surfactants in the form of corresponding soluble salts, rise in the pH of a medium, species ionization and change in electric charges at the system interfaces. The positive influence of these factors favor a decrease in adhesion forces between bitumen and quartz, an increase in electrostatic repulsive forces, separation of bitumen from sand particles and its rise to the aqueous solution surface. Figure 8 shows the microstructure of tar sand and the mechanism of bitumen stripping from sand [10]. The flow diagram for the alkaline leaching recovery of the bitumen is shown in Figure 9.

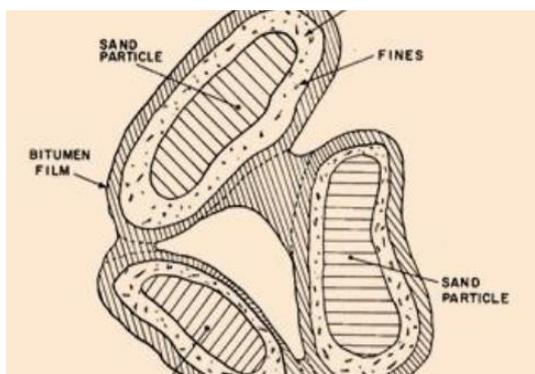


Figure 8. Microstructure of tar sand (Source: Adapted from Takamura [10])

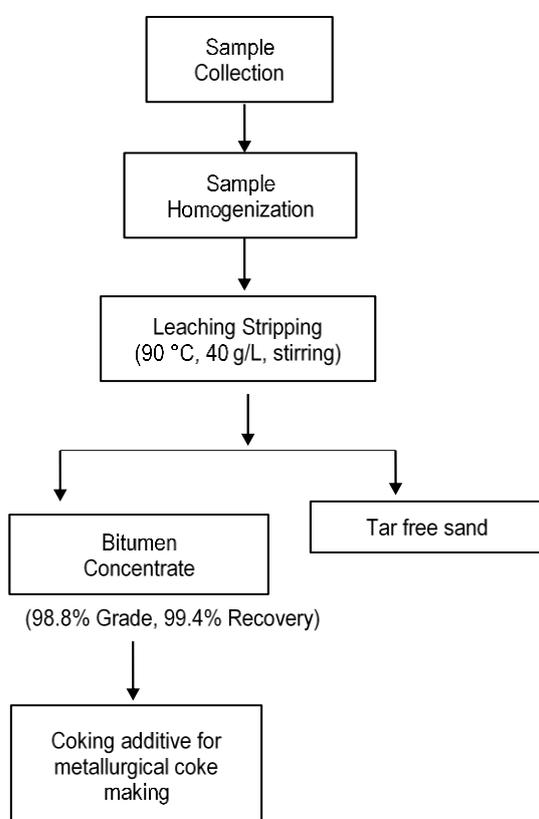


Figure 9. Flow diagram for alkaline leaching extraction of bitumen and the application of the bitumen extract

4. Conclusions

The sand impregnated Ondo tar sand was successfully and optimally stripped of its bitumen content in a stirred condition to produce an ultra-

clean bitumen with grade and recovery percent of 98.82 and 99.41% respectively at combination T_3C_3 , where $T_3 = 90\text{ }^\circ\text{C}$ and $C_3 = 2\text{ M}$ of sodium hydroxide at 30 minutes contact time. The ultra-clean obtained bitumen can serve as raw material input for petroleum products recovery and as a coking additive in blend formulation of coals for metallurgical coke making.

5. References

- [1] Falebita, O.A., Koul, S. (2015) Sustainable development of oil sands and host communities: preliminary system dynamics assessment. In: MakeLearn and TIIM Joint International Conference. Bari, Italy, Proceedings, 2095-2109.
- [2] Erdogan, L. (2011) Dielectric properties of oil sands at 2.45 GHz determined with rectangular cavity resonator. M.Sc. Thesis, University of Montreal, Montreal, QC, Canada.
- [3] Humphries, M. (2008) North American oil sands: history of development, prospects for the future, link of web pages: <https://apps.dtic.mil/dtic/tr/fulltext/u2/a477532.pdf>, (accessed date: 20.06.2019.).
- [4] Strausz, O.P., Lown, E.M. (2003) The chemistry of Alberta oil sands, bitumens and heavy oils. Alberta Energy Research Institute, Calgary, Alberta, Canada, 588-592.
- [5] Schlosberg, R.H., Jordan, R.D., Diefenthal, E.L. (2016) U.S. Patent No. 9,410,089. Washington, D.C: U.S. Patent and Trademark Office.
- [6] Emmanuel, E., Ajibade, O.M. (2014) Elemental Composition and Geochemistry of Heavy Oil in Parts of Eastern Dahomey Basin, Southwestern Nigeria. Journal of Environment and Earth Science, 4 (12), 18-25.
- [7] Adegoke, O.S., Ako, B.D., Enu, E.I. (1980) Geotechnical Investigations of the Ondo State Bituminous Sands, Geology and Reserves Estimate. Unpublished manuscript. Department of Geology, University of Ile-Ife, Nigeria.
- [8] Weskamp, W., Rohde, W., Stewen, W., Habermehl, D. (1987) Greater coke strength through reactive additives to coking blends. In:

- II International Cokemaking Congress. Essen, Germany, Proceedings, 13-18.
- [9] Ryemshak, S.A., Jauro, A., Chindo, I.Y., Ekanem, E.O., Ayeni, F.A. (2015) By-Product from Pyrolysis of Tar-Sand in Blend with Gray-King Assessed Nigerian Coals for Coke Production. International Journal of Chemistry and Materials Research, 3 (11), 154-164.
- [10] Takamura, K., Chow, R.S. (1982) A Mechanism for Initiation of Bitumen Displacement from Oil Sand. In: Annual Technical Meeting, Petroleum Soc. of CIM. Calgary, Canada, 82-83-88.
- [11] SrinivasaRajagopalan, S. (2010) Study of bitumen liberation from oil sands ores. Masters Abstracts International, 49 (2).
- [12] Adeleke, A.A., Ibitoye, S.A., Oladokun, C.B., Oluwasegun, K.M. (2011). An Evaluation of the Hot Aqueous Caustic Leaching of Nigerian Ondo Tar Sand. Petroleum and Coal, 53 (4), 320-323.
- [13] Ghosh, A., Ray, H.S. (1991) Principles of extractive metallurgy. New Age International.

ALKALNA EKSTRAKCIJA ULTRA ČISTOG BITUMENA IZ NAFTNOG PESKA

R.T. Akande^{1#}, A.A. Adeleke¹, P.O. Atanda¹

¹Obafemi Awolowo University, Department of Materials Science and Engineering, Ile-Ife, Nigeria

(Primljen: 27. Avgust 2018.; Prihvaćen: 7. Jun 2019.)

Izvod

U ovom radu je prikazano izdvajanje koncentrata bitumena iz naftnog peska iz države Ondo u Nigeriji postupkom alkalnog luženja. Bitumen je izdvojen iz naftnog peska koji je zagrevan u pećnici i mešan u magnetnoj mešalici sa grejnom pločom na različitim temperaturama dobijenim 3² faktorskim dizajnom pri različitim molarnim koncentracijama natrijum hidroksida i gustine pulpe od 40 g/dm³. Naftni pesak je zatim podvrgnut ispitivanju rastvaranja bitumena, kao i njegovog izdvajanja pri različitim gustinama pulpe. Dobijeni rezultati su pokazali da je optimalno izdvajanje bitumena postignuto iz naftnog peska sa početnim sadržajem bitumena od 34% u mešanom stanju pri čemu se dobija koncentrat kvaliteta 98,82% i iskorišćenje od 99,41% bitumena. Optimalna ekstrakcija luženjem je postignuta kada je koncentracija natrijum hidroksida bila 2 M, temperatura 90 °C, a vreme kontakta 25 minuta. Dobijeni ultra čisti bitumen može da se koristi kao sirovina za dobijanje naftnih derivata, a takođe i kao aditiv za mešavinu uglja koja se koristi prilikom metalurške proizvodnje koksa.

Ključne reči: Naftni pesak; Bitumen; Luženje; Kvalitet; Iskorišćenje; Proizvodnja koksa.